

Magnetic field induced spin-flop transition in Na_xCoO_2 ($0.5 < x < 0.55$)

T. Wu, D. F. Fang, G. Y. Wang, L. Zhao, G. Wu, X. G. Luo, C. H. Wang and X. H. Chen*
*Hefei National Laboratory for Physical Science at Microscale and Department of Physics,
 University of Science and Technology of China, Hefei,
 Anhui 230026, People's Republic of China*

The isothermal magnetoresistance (MR) with magnetic field (H) parallel to and perpendicular to ab plane is systematically studied on the single crystal $\text{Na}_{0.52}\text{CoO}_2$ with charge ordering at ~ 50 K and an in-plane ferromagnetism below 25 K. The isothermal MR behavior with $H \parallel ab$ plane and $H \perp ab$ plane is quite different. When $H \parallel ab$ plane, the MR is always negative and the in-plane ferromagnetic behavior is enhanced. While the MR with $H \perp ab$ plane changes from negative to positive with decreasing temperature or increasing H , and the in-plane ferromagnetic behavior is suppressed. A striking feature is that the MR with $H \perp ab$ plane shows a hysteresis behavior below 25 K, which is absent for the case of $H \parallel ab$ plane. These results provide strong evidence for a spin-flop transition of small moments of $\text{Co}^{3.5-\delta}$ sites induced by $H \perp ab$ plane, leading to a metamagnetic transition for small moments of $\text{Co}^{3.5-\delta}$ sites. These complex magnetism suggests an unconventional superconductivity in Na_xCoO_2 system because the Na_xCoO_2 around $x=0.5$ is considered to be the parent compound of superconductivity.

PACS numbers: 71.27.+a, 74.70.-b, 75.25.+z

The frustrated spin system Na_xCoO_2 has become a focus in research due to the discovery of superconductivity with $T_c \sim 5$ K in $\text{Na}_{0.35}\text{CoO}_2 \cdot 1.3\text{H}_2\text{O}$ ¹. It is believed that strong electronic correlations and the possible novel magnetic ground-states due to geometrical frustration play an important role in the physics, and a rich phase diagram has been reported as a function of the Na concentration². A charge-ordering state is found at $x=0.5$ and novel magnetism is reported for charge-ordering $\text{Na}_{0.5}\text{CoO}_2$ ^{2,3,4}. Recently, the charge-ordering $\text{Na}_{0.5}\text{CoO}_2$ is considered to be the parent compound of superconductivity in this system because the valence of superconductive $\text{Na}_{0.35}\text{CoO}_2 \cdot 1.3\text{H}_2\text{O}$ is found close to $+3.5$ ^{5,6,7}. The superconductivity with the highest T_c was observed in the vicinity of a magnetic phase by many groups^{7,8,9,10}. The understanding of the novel magnetism is believed to shed light on the mechanism of superconductivity.

NMR and neutron diffraction studies have given spin structure for the charge ordering $\text{Na}_{0.5}\text{CoO}_2$ ^{3,4}. They reported that there exist two kinds of Co sites with large and small magnetic moments in $\text{Na}_{0.5}\text{CoO}_2$. The large moments of $\text{Co}^{3.5+\delta}$ sites align antiferromagnetically at $T_{c1} \sim 87$ K with spin direction within ab plane, while the small magnetic moments $\text{Co}^{3.5-\delta}$ sites align along the direction parallel to the c -axis. It cannot be distinguished if the in-plane spin correlation of the small moment sites is ferromagnetic or antiferromagnetic. Recently, our group *et al.*¹¹ found a six-fold symmetry in angular dependent in-plane magnetoresistance below a certain temperature (T_p) for charge-ordering $\text{Na}_{0.34}(\text{H}_3\text{O})_{0.15}\text{CoO}_2$ sample. It gives a definite evidence that the small mo-

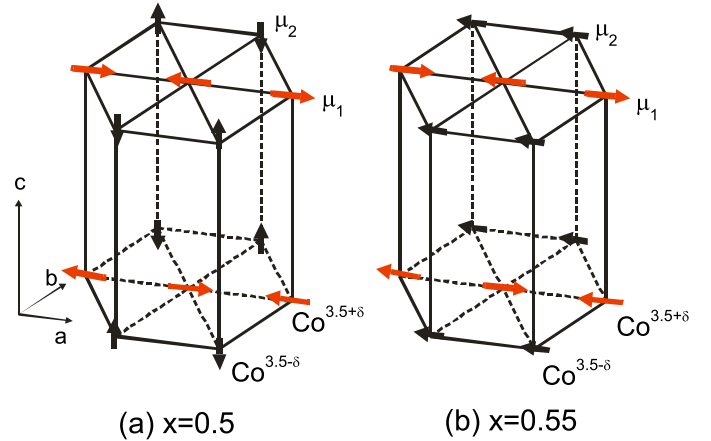


FIG. 1: Magnetic structure for Na_xCoO_2 : (a) $x=0.5$ from Ref. [3, 11]; (b) $x=0.55$ from Ref. [12].

ments of $\text{Co}^{3.5-\delta}$ sites align antiferromagnetically with spin direction along c axis. The magnetic structure for $\text{Na}_{0.5}\text{CoO}_2$ is shown in Fig.1(a). Subsequently, Wang *et al.* have found in-plane ferromagnetism below 17 K in $\text{Na}_{0.55}\text{CoO}_2$ which enriches the magnetic phase diagram around $x=0.5$ ¹². We found that the small moments of $\text{Co}^{3.5-\delta}$ sites align ferromagnetically in ab plane, and the large moments of $\text{Co}^{3.5+\delta}$ sites still align antiferromagnetically in ab plane. The magnetic structure proposed by Wang *et al.* is shown in Fig. 1(b). This result suggests that a spin-flop transition of the small moments of $\text{Co}^{3.5-\delta}$ sites takes place with slight change of Na content around $x=0.5$, and the magnetic coupling of small moments of $\text{Co}^{3.5-\delta}$ sites changes from antiferromagnetic for $x=0.5$ to ferromagnetic for $x=0.55$. Further investigation

*Corresponding author; Electronic address: chenxh@ustc.edu.cn

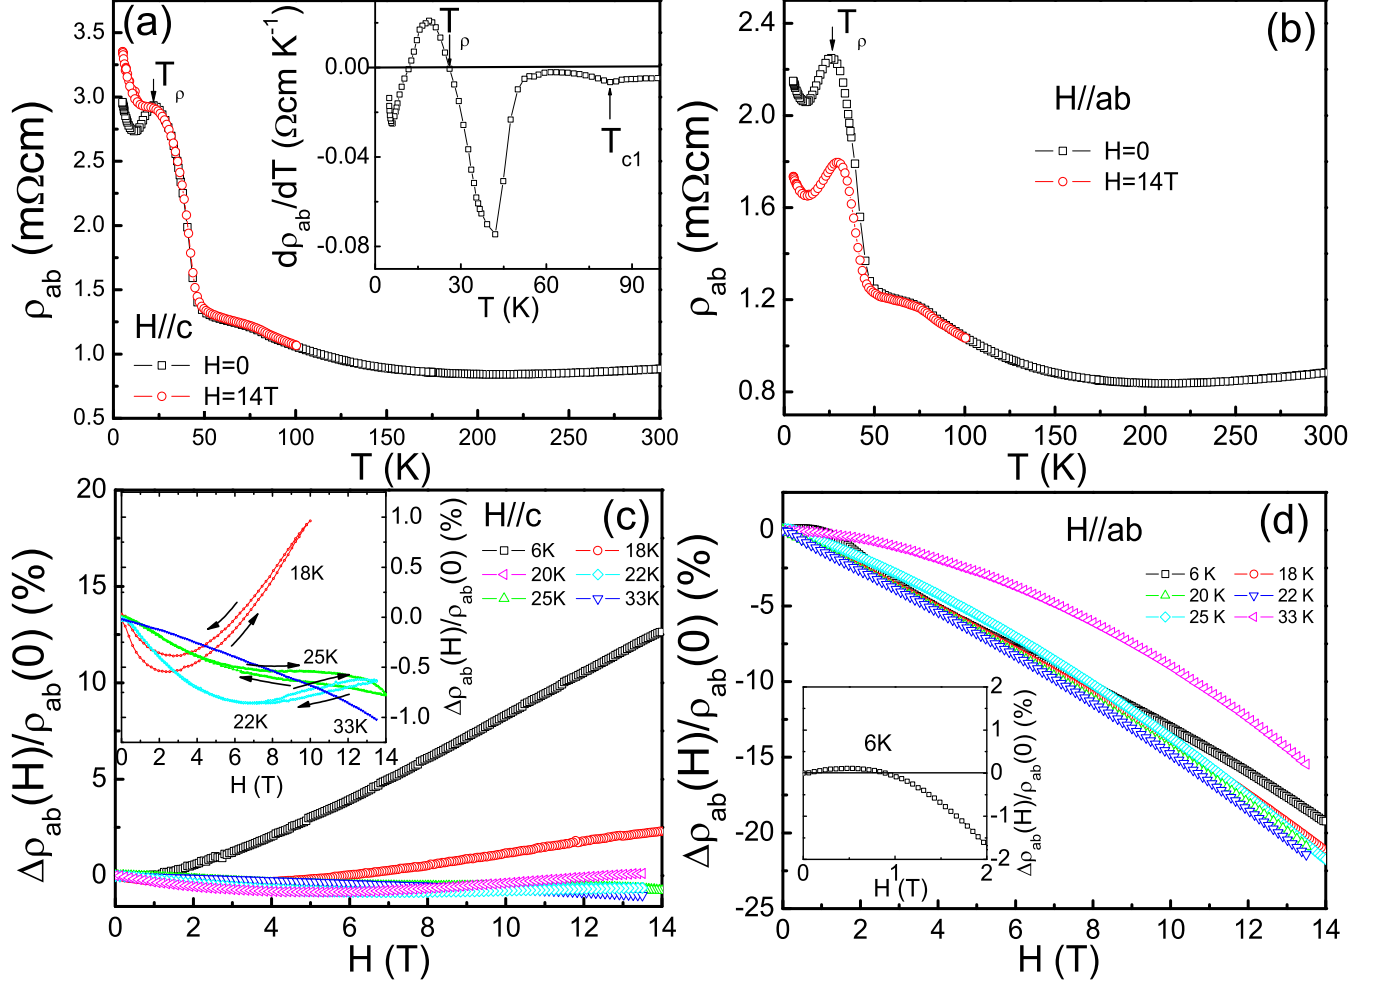


FIG. 2: (color online). Temperature dependence of in-plane resistivity under different fields with (a) $H \perp \text{Co-O plane}$ and (b) $H \parallel \text{Co-O plane}$; isothermal magnetoresistance with (c) $H \perp \text{Co-O plane}$ and (d) $H \parallel \text{Co-O plane}$. The inset in (a) and (c) shows $d\rho_{ab}/dT$ with $H=0$ and the isothermal MR hysteresis, respectively.

of the evolution of magnetism in this region is needed to understand these intriguing magnetic properties, which is helpful to understand the mechanism of superconductivity and novel magnetic ground states in this frustrated spin system.

Magnetoresistance (MR) provides insight into the coupling between charge and background magnetism. This is particularly valuable because, as shown in previous work¹¹, small magnetic moments order in the background of magnetic ordering with large magnetic moments, and such ordering is difficult to detect by magnetization measurement. In this paper, we systematically study MR for the Na_xCoO_2 crystals with x between 0.5 and 0.55. The MR is defined by $\text{MR} = \frac{\rho(H) - \rho(0)}{\rho(0)} = \frac{\Delta\rho(H)}{\rho(0)}$. An in-plane ferromagnetism is observed below 25 K. Isothermal MR shows quite different behaviors between $H \perp ab$ plane and $H \parallel ab$ plane. A magnetic field induced spin-flop transition of small moments of $\text{Co}^{3.5-\delta}$ sites is proposed to explain these complex phenomena.

High quality single crystals $\text{Na}_{0.7}\text{CoO}_2$ were grown using the flux method. The typical dimension is about $2 \times 1.5 \times 0.01 \text{ mm}^3$ with the shortest dimension along the c axis. The $\text{Na}_{0.52}\text{CoO}_2$ sample is prepared by sodium deintercalation of the $\text{Na}_{0.7}\text{CoO}_2$ single crystals. The procedure is similar to the way to prepare the $\text{Na}_{0.55}\text{CoO}_2$ sample; the difference is that a longer reaction time is needed for the same concentration compared to the preparation of $\text{Na}_{0.55}\text{CoO}_2$. About 5 mg of $\text{Na}_{0.7}\text{CoO}_2$ single crystals were immersed in the sealed conical flask with 5 ml 0.15 M solution of I_2 in acetonitrile at room temperature for about 40 hours. The x values of the samples were estimated by the lattice parameter c determined by X-ray diffraction. The resistance was measured by an AC resistance bridge (LR-700, Linear Research). A superconducting magnet system (Oxford Instruments) was used to achieve magnetic field up to 14 T. Temperature measurement used a magnetic field insensitive temperature sensor (CERNOX, Lakeshore Cryotronics). It

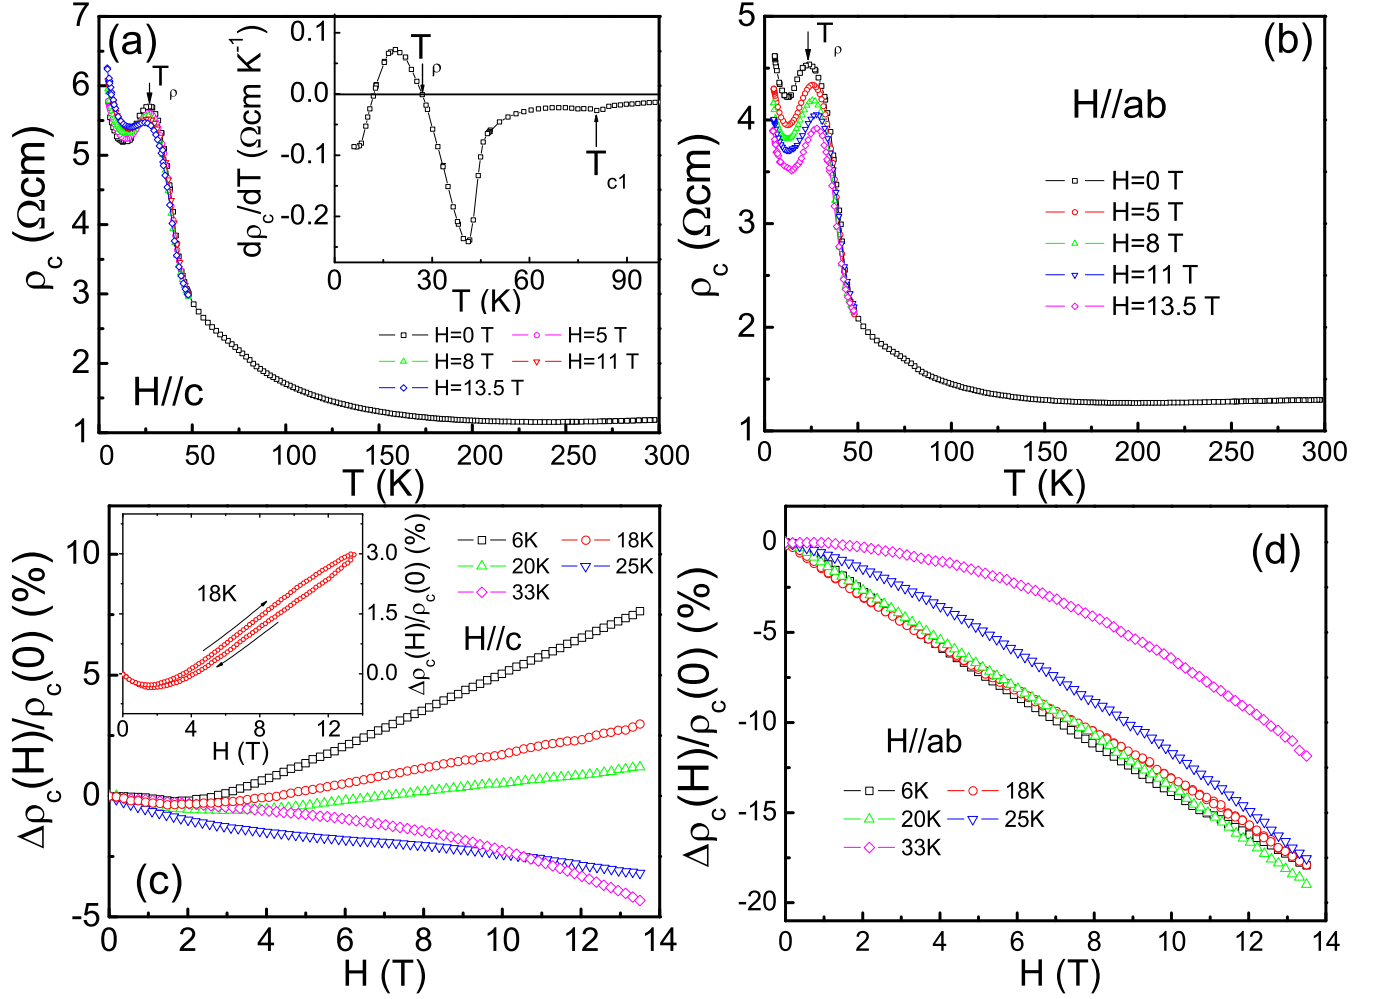


FIG. 3: (color online). Temperature dependence of out-of-plane resistivity under different fields with (a) $H \perp$ Co-O plane and (b) $H \parallel$ Co-O plane; isothermal magnetoresistance with (c) $H \perp$ Co-O plane and (d) $H \parallel$ Co-O plane. The inset in (a) and (c) shows $d\rho_c/dT$ with $H=0$ and the isothermal MR hysteresis, respectively.

should be addressed that all results discussed as follow are well reproducible.

Fig. 2 shows the in-plane resistivity and magnetoresistance for $H \parallel ab$ plane and $H \perp ab$ plane, respectively. As shown in Fig. 2(a), the zero-field resistivity shows charge ordering behavior at ~ 50 K and a kink at 25 K, being similar behavior as that of the in-plane ferromagnetic $\text{Na}_{0.55}\text{CoO}_2$ ¹². The transition of the slope $d\rho/dT$ from negative to positive around 25 K (T_ρ) is believed to arise from the in-plane ferromagnetic ordering for the small moments of $\text{Co}^{3.5-\delta}$ sites¹². A rapid upturn around 50 K should be due to the charge ordering as that in $\text{Na}_{0.5}\text{CoO}_2$. In addition, another anomaly in slope $d\rho/dT$ is observed at 83 K which corresponds to the antiferromagnetic ordering temperature (T_{c1}) as the case of $\text{Na}_{0.5}\text{CoO}_2$. The temperature in $\text{Na}_{0.55}\text{CoO}_2$ and $\text{Na}_{0.50}\text{CoO}_2$ is 77 K and 87 K, respectively. It further indicates that the Na content of the current sample is between $x=0.5$ and $x=0.55$, consistent with single crys-

tal XRD result. In Fig. 2(a) and (b), resistivity under 14 T shows different behavior below T_ρ with different field direction. When $H \perp ab$ plane, T_ρ is independent on H and the in-plane ferromagnetic behavior is suppressed below T_ρ . Descending of resistivity due to in-plane ferromagnetism is killed and an upturn in resistivity below T_ρ is induced by magnetic field $H \perp ab$ plane, so that the resistivity shows similar behavior to that of $\text{Na}_{0.5}\text{CoO}_2$. When $H \parallel ab$ plane, T_ρ increases with H and the charge-ordering behavior is suppressed. Similar behavior is also observed in $\text{Na}_{0.5}\text{CoO}_2$ with high magnetic field as high as 45 T by Balicas *et al.*¹³. They found that the field $H \perp ab$ plane enhances the charge-ordering state and the field $H \parallel ab$ plane strongly suppresses the charge-ordering state.

The MR for $H \parallel ab$ plane and $H \perp ab$ plane in Fig. 2(c) and (d) shows different MR behavior. When $H \parallel ab$ plane, the isothermal MR is negative and monotonously increases with H . The magnitude of MR below T_ρ is al-

most temperature independent with varying H , and as high as 22% under $H=13.5$ T at 20 K just below T_ρ . MR at 6 K is positive below 1 T and changes to negative with increasing H as shown in the inset of Fig. 2(d). The positive part at low field is considered to come from antiferromagnetic background of large moments of $\text{Co}^{3.5+\delta}$ sites, and the negative part from contribution of in-plane ferromagnetic of small moments of $\text{Co}^{3.5-\delta}$ sites overwhelms the positive part at high field. When $H \perp ab$ plane, a crossover from negative to positive with increasing H is observed in the isothermal MR. At 6 K, the MR is always positive and as high as 12.5% under 13.5 T. Compared to resistivity under magnetic field and MR of $\text{Na}_{0.5}\text{CoO}_2$ ¹⁴ and $\text{Na}_{0.55}\text{CoO}_2$ ¹², the results of resistivity under H and MR indicate that the magnetic coupling of small moments of $\text{Co}^{3.5-\delta}$ sites can be changed by magnetic field perpendicular to ab plane from ferromagnetic to antiferromagnetic. An intriguing MR hysteresis phenomenon is found below T_ρ with increasing H to 14 T and then decreasing to zero. The inset in Fig. 2(c) shows the irreversible behavior. Below T_ρ , the MR hysteresis is induced by $H \perp ab$ plane. The critical field (H_C) is temperature dependent. Above T_ρ , the hysteresis phenomenon is not observed with H as high as 14 T, indicating that the hysteresis is related to in-plane ferromagnetism. In addition, the direction of hysteresis varies with decreasing T . At 22 K and 25 K, the direction is clockwise. But the direction is anti-clockwise at 18 K. Such hysteresis is absent for $H \parallel ab$ plane. These phenomena can be explained with a spin-flop transition of small moments of $\text{Co}^{3.5-\delta}$ induced by the magnetic field perpendicular to ab plane. The spin-flop transition makes the magnetic state from in-plane ferromagnetic to antiferromagnetic state. The hysteresis is caused by the different spin-flop energy of $\text{FM} \rightarrow \text{AF}$ ($E_{\text{FM} \rightarrow \text{AF}}$) and $\text{AF} \rightarrow \text{FM}$ ($E_{\text{AF} \rightarrow \text{FM}}$). The difference of hysteresis direction between 18 K and 22 K suggests that the relation of $E_{\text{FM} \rightarrow \text{AF}}$ and $E_{\text{AF} \rightarrow \text{FM}}$ is changed with decreasing T .

The out-of-plane resistivity ρ_c under H and the isothermal out-of-plane MR are also studied. Fig. 3 shows the out-of-plane magnetotransport and the isothermal out-of-plane MR with $H \parallel ab$ plane and $H \perp ab$ plane, respectively. The values of T_ρ and T_{c1} are the same as that of in-plane. The effect of magnetic field on ρ_c is quite similar to that on ρ_{ab} although the out-of-plane MR is less than the in-plane MR. Similar to the in-plane behavior, T_ρ is not affected by H applied along c axis, while T_ρ is enhanced by H parallel to the ab plane. The charge-ordering behavior is suppressed by $H \parallel ab$ plane and enhanced by $H \perp ab$ plane. The behavior of isothermal out-of-plane MR is also similar to that of the in-plane MR, and the MR hysteresis is also observed only when $H \perp ab$ plane. These results further confirm the spin-flop transition in this system.

The spin-flop transition for small moments of $\text{Co}^{3.5-\delta}$ leads to the metamagnetism. Such metamagnetism is difficult to detect by susceptibility measurements because small magnetic moments order in the background

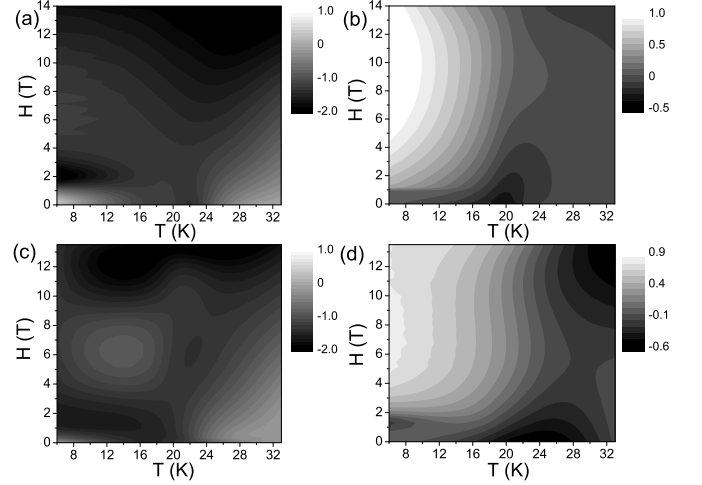


FIG. 4: 2D project picture of derivation of MR dependent H and T . (a): in-plane derivation of MR with $H \parallel \text{Co-O}$ plane; (b): in-plane derivation of MR with $H \perp \text{Co-O}$ plane; (c): out-of-plane derivation of MR with $H \parallel \text{Co-O}$ plane; (d): out-of-plane derivation of MR with $H \perp \text{Co-O}$ plane.

of magnetic ordering with large magnetic moments. To further understand the spin-flop transition, a formula consisting of negative and positive contributions to MR, $-A_1^2 \ln(1+A_2^2 H^2) + B^2 H^n$, is used to qualitatively describe MR. The first term in the formula is derived from the third-perturbation expansion of s-d exchange Hamiltonian in the local magnetic moment model of Toyozawa^{15,16}. The formula has been used to explain the isothermal MR behavior for $\text{Na}_{0.55}\text{CoO}_2$ ¹² and another triangle lattice cobalt oxide $(\text{Bi,Pb})_2\text{Sr}_2\text{Co}_2\text{O}_y$ ¹⁷. Here, the negative part is due to the contribution of in-plane magnetism ordered by small moments of $\text{Co}^{3.5-\delta}$ sites. When the magnetic coupling of small moments of $\text{Co}^{3.5-\delta}$ sites is changed from ferromagnetic to antiferromagnetic due to spin-flop transition induced by $H \perp ab$ plane, the contribution of negative part to MR is changed. A 2D project picture of $\frac{dMR}{dH}$ is plotted in Fig. 3. The in-plane $\frac{dMR}{dH}$ with $H \parallel ab$ plane and $H \perp ab$ plane is shown in Fig. 4(a) and (b), respectively. The black region and white region stand for negative and positive slope $\frac{dMR}{dH}$, respectively. It is found that the negative maximum of the slope changes continuously for $H \parallel \text{Co-O}$ plane and discontinuously for $H \perp ab$ plane with decreasing temperature around the T_ρ . We believe that these differences are due to metamagnetism induced by magnetic field perpendicular ab plane. The derivation of the negative part is $-\frac{2A_1^2 A_2^2}{1+A_2^2 H^2}$. When $H = \frac{1}{A_2}$, the $\frac{dMR}{dH}$ reach to the maximum. Khosla *et al.*¹⁵ gave the expression of $A_2: \frac{\lambda}{T}$, $\lambda = F(J)$. The parameter J is s-d exchange integral. It suggests that the maximum of $\frac{dMR}{dH}$ can be changed by variety of exchange integral. Therefore, the discontinuity in $\frac{dMR}{dH}$ may come from the change of magnetic coupling under s-d exchange model. It suggests

that the field $H \perp ab$ plane can induce antiferromagnetic coupling of small moments of $\text{Co}^{3.5-\delta}$ sites below T_ρ , which is corresponding to distinct change of the exchange integral. The white region covers large area with $H \perp ab$ plane and the transition point H_c ($\frac{dMR}{dH}|_{H_c}=0$) is dependent on temperature. No apparent transition from negative slope to positive slope is observed with $H \parallel ab$ plane. These results confirm that the field $H \perp ab$ plane can induce antiferromagnetic coupling and the field $H \parallel ab$ plane enhances the in-plane ferromagnetism. The out-of-plane $\frac{dMR}{dH}$ is shown in Fig. 4(c) and (d), respectively. Similar behavior to the in-plane case is observed for out-of-plane $\frac{dMR}{dH}$.

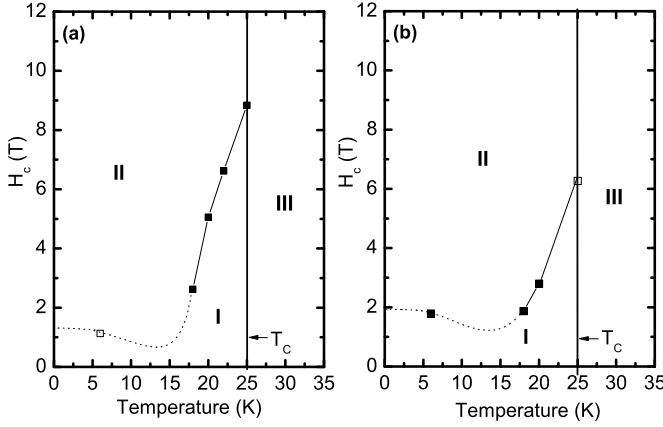


FIG. 5: Phase diagram for the spin of $\text{Co}^{3.5-\delta}$ in $\text{Na}_{0.52}\text{CoO}_2$ with magnetic field perpendicular to ab plane and temperature. (a): derived from in-plane data; (b): derived from out-of-plane data. I region: in-plane ferromagnetic region; II region: spin flop region; III region: paramagnetic region. Open square is determined by the kink of $\frac{dMR}{dH}$ and filled square is determined by $\frac{dMR}{dH}=0$

Based on the results that a spin-flop for small moments of $\text{Co}^{3.5-\delta}$ sites is induced by $H \perp ab$ plane and the in-plane ferromagnetism is suppressed, a H - T phase diagram with $H \perp ab$ plane is derived as shown in Fig. 5. Three different magnetic regions of small moments of $\text{Co}^{3.5-\delta}$ sites are defined in H - T phase diagram: a) I: In-plane ferromagnetic region; b) II: spin-flop region; c) III: paramagnetic region. The boundary of I and II region is determined by $\frac{dMR}{dH}=0$. The maximum of H_c is 8.8 T for in-plane resistivity and 6.3 T for out-of-plane resistivity, respectively. This phase diagram indicates the instability of in-plane ferromagnetism with magnetic field $H \perp ab$ plane. This instability suggests the existence of novel magnetic ground state in this spin frustrated system around $x=0.5$.

The characteristics of spin-flop in Na_xCoO_2 have been also reported for high Na content^{18,19,20}. The neutron scattering studies on $\text{Na}_{0.82}\text{CoO}_2$ ¹⁸ and $\text{Na}_{0.75}\text{CoO}_2$ ^{19,20} indicate that the in-plane and inter-plane spin correlations are ferromagnetic and antiferromagnetic, respectively, and all the spins align along the c axis. These re-

sults indicate that a spin-flop transition takes place with decreasing Na content; that is, the spin direction changes from along c axis to within ab plane. In $\text{Na}_{0.85}\text{CoO}_2$, a magnetic field induced spin-flop has been reported by Luo *et al.*²¹. Analogously, magnetic field induced spin-flop transition of the small moments of $\text{Co}^{3.5-\delta}$ sites occurs in our samples below T_ρ . When $H \perp ab$ plane, the small moments of $\text{Co}^{3.5-\delta}$ sites flop to c axis and the magnetic coupling changes from ferromagnetic to antiferromagnetic. When $H \parallel ab$ plane, the in-plane ferromagnetism is enhanced. As shown in Fig. 5, the spin-flop transition occurs with decreasing temperature or increasing magnetic field.

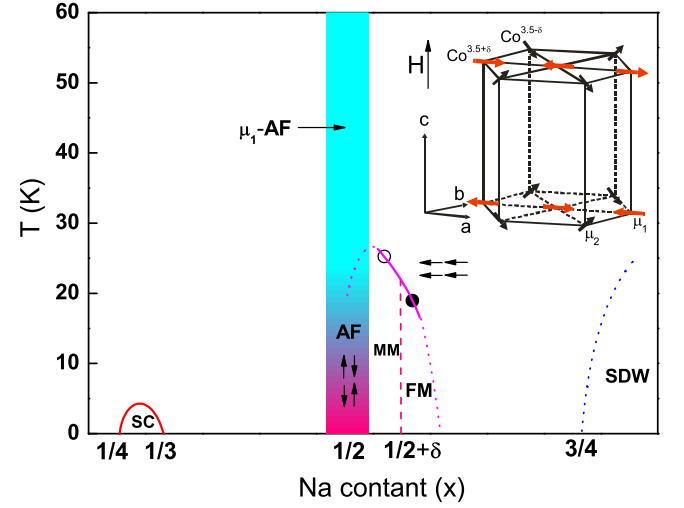


FIG. 6: The renewed magnetic phase diagram of Na_xCoO_2 . The μ_1 -AF, AF, FM, MM, SC and SDW stand Antiferromagnetism of $\text{Co}^{3.5+\delta}$, Antiferromagnetism of $\text{Co}^{3.5-\delta}$, Ferromagnetism of $\text{Co}^{3.5-\delta}$, Metamagnetism of $\text{Co}^{3.5-\delta}$, Superconductivity and Spin density wave respectively. The open and filled circles stand for the ferromagnetic transition point for $\text{Na}_{0.52}\text{CoO}_2$ and $\text{Na}_{0.55}\text{CoO}_2$, respectively. The right corner magnetic structure is proposed for $x=0.55$ with field $H \perp ab$ plane.

Based on the results for $x=0.5$ and 0.55 reported by us^{11,12}, we renew the phase diagram around $x=0.5$ as shown in Fig. 6. At $x=0.5$, the magnetic coupling of the small moments of $\text{Co}^{3.5-\delta}$ sites are antiferromagnetic and the direction of magnetic moments is along c axis. With increasing Na content, the small moments of $\text{Co}^{3.5-\delta}$ sites flop to ab plane and the magnetic coupling changes to ferromagnetic. For the samples with x between $x=0.5$ and 0.55 , magnetic field can induce spin-flop transition. Because the spin-flop transition is accompanied with the change of magnetic coupling, this region can be defined as Metamagnetic region (MM). The magnetic structure for this region with field $H \perp ab$ plane is shown in Fig. 6. Many different groups^{7,8,9,10} have revised the superconducting phase. It is found that the superconductivity with the highest T_C is observed in the vicinity of a magnetic phase,

strongly suggesting that magnetic fluctuations play an important role in the occurrence of superconductivity^{9,10}. The valence of our sample is closed to +3.48 in the superconductor $\text{Na}_{0.337}(\text{H}_3\text{O})_{0.234}\text{CoO}_2 \cdot y\text{H}_2\text{O}$. Therefore, our result suggests that there exists strong correlation between the superconductivity and novel magnetism around $x=0.5$. Recently, a nesting scenario for charge-ordering $\text{Na}_{0.5}\text{CoO}_2$ has been proposed by NMR and ARPES result^{22,23}. The nesting leads to either spin density wave (SDW) or charge density wave at low temperature which opens a gap on the nested parts of the fermi surface. When the in-plane ferromagnetic is replaced by antiferromagnetic coupling with field $H \perp ab$ plane, the charge-ordering behavior is enhanced in $\text{Na}_{0.52}\text{CoO}_2$ as shown in Fig. 1 and Fig. 2. Therefore, our result provides indirect evidence to this nesting scenario. In addition, this instability of fermi surface is considered to lead to unconventional superconductivity.

In conclusion, the isothermal MR for the Na_xCoO_2 crystals with x between 0.5 and 0.55 is systematically studied. An in-plane ferromagnetism is observed below

25 K. When $H \perp ab$ plane, the in-plane ferromagnetism is suppressed and the antiferromagnetism of small moments of $\text{Co}^{3.5-\delta}$ sites is enhanced, so that the resistivity shows similar behavior to that observed in $\text{Na}_{0.5}\text{CoO}_2$. A striking feature is observed that a MR hysteresis below the Curie temperature occurs with $H \perp ab$ plane. A magnetic field induced spin-flop transition of small moments of $\text{Co}^{3.5-\delta}$ sites can explain these complex phenomena well. Although the sample $\text{Na}_{0.52}\text{CoO}_2$ shows the same in-plane ferromagnetism as that of $\text{Na}_{0.55}\text{CoO}_2$, their resistivity under H and MR show quite different behavior. It further indicates that the complicated magnetic structure around $x=0.5$ is very sensitive to the Na content. Under the nesting scenario, the instability in magnetism is related to the instability of fermi surface, which is considered to lead to unconventional superconductivity.

This work is supported by the grant from the Nature Science Foundation of China and by the Ministry of Science and Technology of China (973 project No: 2006CB601001 and 2006CB0L1205).

-
- ¹ K. Takada et al., Nature (London) **422**, 53(2003).
 - ² M. L. Foo et al., Phys. Rev. Lett. **92**, 247001(2004).
 - ³ M. Yokoi et al., J. Phys. Soc. Jpn. **74**, 3046(2005).
 - ⁴ G. Gasparovic et al., Phys. Rev. Lett. **96**, 046403(2006).
 - ⁵ K. Takada et al., J. Mater. Chem. **14**, 1448(2004).
 - ⁶ P. W. Barnes et al., Phys. Rev. B **72**, 134515(2005).
 - ⁷ H. Sakurai et al., cond-mat/0511416.
 - ⁸ C. J. Milne et al., Phys. Rev. Lett. **93**, 247007(2004).
 - ⁹ H. Sakurai et al., J. Phys. Soc. Jpn. **74**, 2909(2005).
 - ¹⁰ Y. Ihara et al., J. Phys. Soc. Jpn. **74**, 867(2005).
 - ¹¹ C. H. Wang et al., Phys. Rev. B **74**, 172507(2006).
 - ¹² C. H. Wang et al., Phys. Rev. Lett. **96**, 216401(2006).
 - ¹³ L. Balicas et al., Phys. Rev. Lett. **94**, 236402(2005).
 - ¹⁴ C. H. Wang et al., Phys. Rev. B **71**, 224515(2005).
 - ¹⁵ R. P. Khosla et al., Phys. Rev. B **2**, 4084(1970).
 - ¹⁶ Y. Toyozawa, J. Phys. Soc. Jpn. **17**, 986(1962).
 - ¹⁷ X. G. Luo et al., Eur. Phys. J. B **49**, 37(2006).
 - ¹⁸ S. P. Bayrakci et al., Phys. Rev. Lett. **94**, 157205(2005).
 - ¹⁹ A. T. Boothroyd et al., Phys. Rev. Lett. **92**, 197201(2004).
 - ²⁰ L. M. Helme et al., Phys. Rev. Lett. **94**, 157206(2005).
 - ²¹ J. L. Luo et al., Phys. Rev. Lett. **93**, 187203(2004).
 - ²² D. Qian et al., Phys. Rev. Lett. **96**, 046407(2006).
 - ²³ J. Bobroff et al., Phys. Rev. Lett. **96**, 107201(2006).